

NASNM15M

Non-Magnetic High-Strength Stainless Steel

A high-manganese austenitic stainless steel, NASNM15M was developed by Nippon Yakin with a composition of 17Cr-15Mn-4Ni. Providing higher strength than conventional non-magnetic austenitic stainless steels, NASNM15M does not magnetize even if cold worked with force. Nippon Yakin supplies this product in plate, sheet and strip forms.

Steel Grade/Standard

Nippon Yakin Grade	JIS	ASTM
NASNM15M	—	—

Chemical Composition

	C	Si	Mn	P	S	Ni	Cr	N
Specification (NASNM15M)	0.040~0.090	≤0.90	14.00~15.00	≤0.045	≤0.015	4.00~4.60	16.50~17.50	0.30~0.35

Physical Properties

Density	[g/cm ³]	8.00
Specific heat	[J/kg · K]	480
Electrical resistivity	[μΩ · cm]	77
Thermal conductivity	[W/m · K]	13.2
Average coefficient of thermal expansion [10 ⁻⁶ /°C]	30~100°C	16.0
	30~300°C	17.7
	30~500°C	19.2
	30~700°C	20.3
Young's modulus	[MPa]	19.6 × 10 ⁴
Magnetism		None
Melting range	[°C]	1360~1412



NIPPON YAKIN KOGYO CO., LTD.


Mechanical Properties

Mechanical Properties at Room Temperature



		0.2% proof stress [MPa]	Tensile strength [MPa]	Elongation [%]	Hardness [HV]
Specification (NASNM15M)		≥ 390	≥ 690	≥ 30	≤ 240
Example	Cold-rolled sheet	461	789	45	211

High Temperatures Strength

Results of high-temperature tensile test

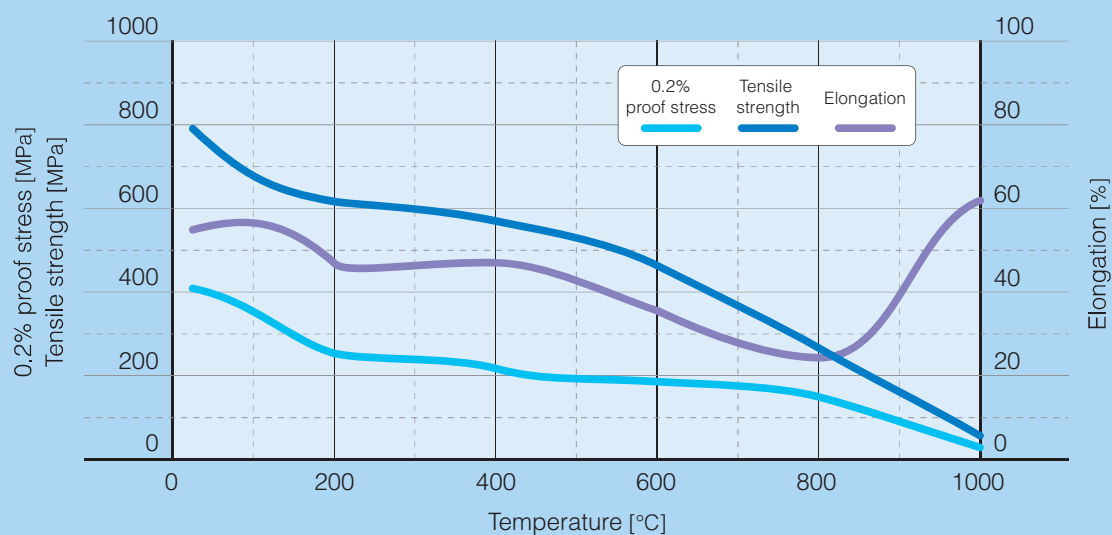


Work Hardening

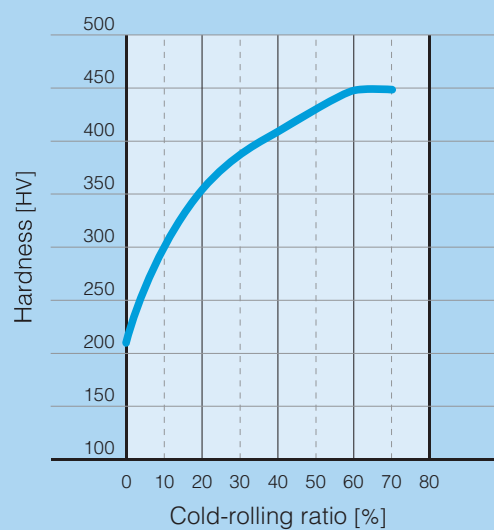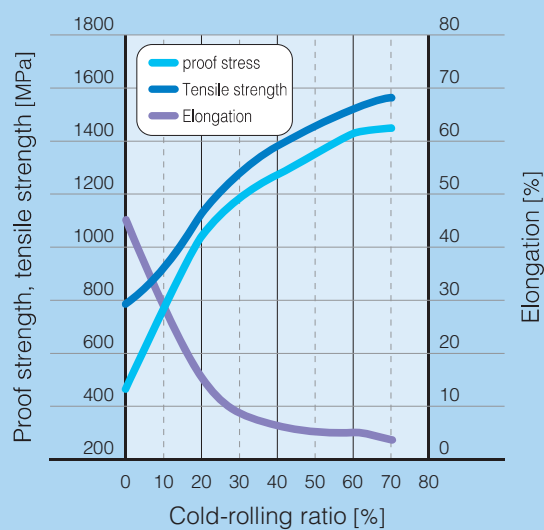


Permeability

Even when cold working is applied, there is no variation in the relative permeability, and NASNM15M does not become magnetized.

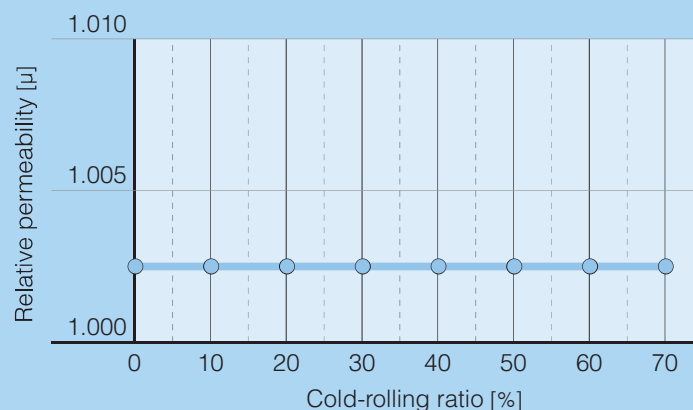

Age Hardening Behavior

After cold-rolling, the hardness of NASNM15M can be raised to between 50 and 70 Hv with heat treatment between 300 and 500°C.

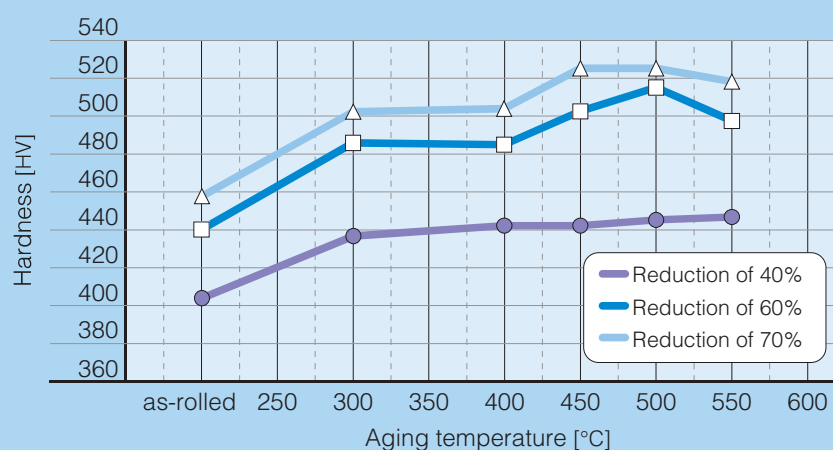

Corrosion Resistance

Just as with the standard austenitic stainless steel Type 304, the corrosion resistance of NASNM15M shows no degradation even after strong cold working.

Evaluation of Pitting Corrosion Resistance

Test condition: 5% NaCl, 30°C

Solution-treated NASNM15M	0.34V
60% cold-rolled NASNM15M	0.31V

Atmospheric Corrosion Resistance in Salt Spray Test

Test condition: 5% NaCl, 35°C for 7 days

Solution-treated NASNM15M	No rusting
60% cold-rolled NASNM15M	No rusting

Workability

The hot and cold workability of NASNM15M is basically the same as that of standard austenitic stainless steels such as Type 304, Type 316, etc. However, the fact that this is a high strength material must be considered in both cold and hot working.

Heat Treatment

The heat treatment is similar to austenitic stainless steels. The typical heat treatment is as follows:

Solution heat treatment: 1030~1150°C; rapid cooling

Applications

Non-magnetic springs, Electronic components, Components in which a non-magnetic property is required.

For more information, please contact:

Nippon Yakin Kogyo Co., Ltd.

Material Solutions Sales Department

San-Ei Bldg., 5-8, 1-chome Kyobashi, Chuo-ku,

Tokyo 104-8365 Japan

TEL: +81-3-3273-4649 FAX: +81-3-3273-4642

URL: <https://www.nyk.co.jp/en/>

Note regarding the handling of property data:

The technical information contained in this product guide is representative values obtained in property tests and other items used to explain the performance of the product. With the exception of items specifically mentioned as provisions of a "Standard," the contents do not represent guaranteed upper limit or lower limit values. The respective data given on this technical information are typical examples and may be different in some cases from the data obtained from the actual product. No responsibility shall, therefore, be assumed for damages arising from using the technical information data. This information is also subject to change in the future without notice. To obtain the most recent information, please contact Nippon Yakin. No part of this document may be copied or reproduced in any form without the consent of Nippon Yakin.